

Industrial Coatings

Technical Data Sheet



We create chemistry

Joncryl[®] 935 Polyol

Product Description	Joncryl [®] 935 is an acrylic polyol for polyurethane coating applications.
Key Features & Benefits	<ul style="list-style-type: none">- Excellent curability- Chemical resistance- Fast dry time
Chemical Composition	Acrylic polyol

Properties

Typical Properties	Appearance	clear liquid
	Non-volatile at 150°C (0.5g, 60 minutes)	~ 70%
	Hydroxyl number of solids	~ 150
	Viscosity at 25.0 ± 0.5°C (Brookfield #4LV, 30 rpm, 60 seconds)	4,000 – 13,000 cP
	Density at 20°C	~ 1.03 g/cm ³ (8.55 lbs/gal)
	Equivalent weight as supplied, of solids	~ 535, 375
	Tg	~ 17°C
	Solvent	Methyl n-amyl ketone

These typical values should not be interpreted as specifications.

Applications


Joncryl[®] 935 is a high performance polyol for polyurethane coatings suitable for automotive refinish and industrial applications. It offers excellent exterior durability with good chemical resistance.

Joncryl[®] 935 is recommended for applications such as:

- Interior/exterior general metal coating applications
- Automotive refinish applications

South Florida Weathering

The following graph demonstrates the 60° gloss retention of polyurethane coating formulations based on Joncryl® 935 in South Florida weathering (ASTM G7-05). No UV stabilizers were used.

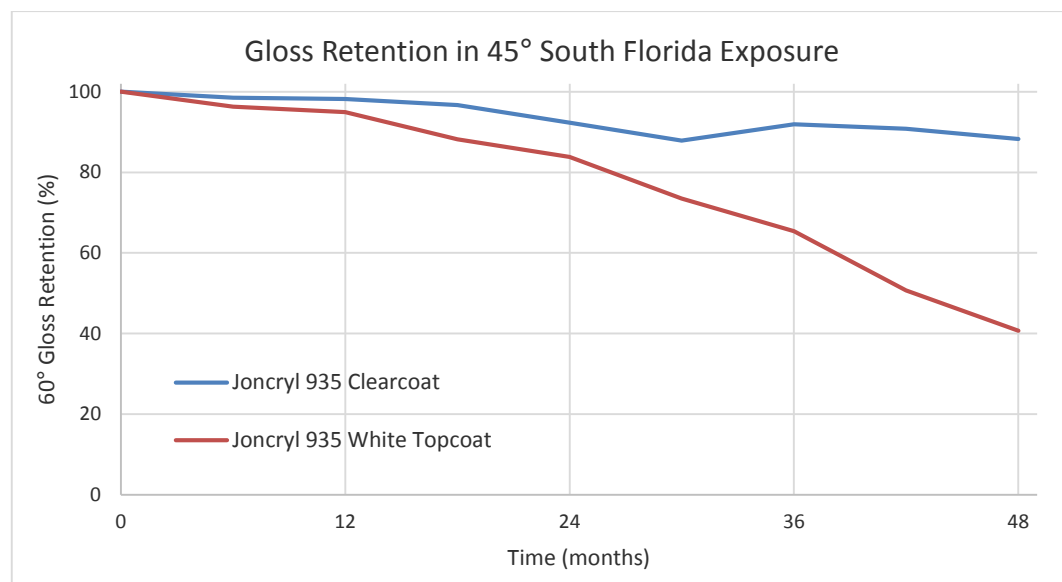

Starting Point Formulation

The following starting point formulations is recommended for an initial evaluation of Joncryl® 935. Additional optimization of the formulation may be required to achieve desired results for specific applications.

Joncryl® 935 CLEAR , Formula 1053111-02-15

Part A	Pounds	Gallons
Joncryl® 935	445.80	51.84
MAK	178.77	26.29
Efka® FL 3670	0.74	0.09
25% CAB ¹ -551-0.01 in n-BA	<u>33.97</u>	<u>4.62</u>
Subtotal	659.28	82.84
Part B		
Basonat® HI 100	<u>166.96</u>	<u>17.16</u>
Total	826.24	100.00

Formulation Attributes

Non-volatile	59.09% by wt, 50.30% by volume
Viscosity (A + B)	198 cP
NCO:OH ratio	1.05:1
Mix ratio by volume	4.83:1
Weight per gallon	8.26 lbs
VOC (calculated)	3.38 lbs/gal, 405.04 g/l

¹Registered trademark of Eastman Chemical Company.

Safety

General

The usual safety precautions when handling chemicals must be observed. These include the measures described in Federal, State, and Local health and safety regulations, thorough ventilation of the workplace, good skin care, and wearing of personal protective equipment.

Safety Data Sheet

All safety information is provided in the Safety Data Sheet for Joncryl® 935.

Important

While the descriptions, designs, data and information contained herein are presented in good faith and believed to be accurate, they are provided for guidance only. Because many factors may affect processing or application/use, BASF recommends that the reader make tests to determine the suitability of a product for a particular purpose prior to use. **NO WARRANTIES OF ANY KIND, EITHER EXPRESSED OR IMPLIED, INCLUDING, BUT NOT LIMITED TO, WARRANTIES OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE, ARE MADE REGARDING PRODUCTS DESCRIBED OR DESIGNS, DATA OR INFORMATION SET FORTH, OR THAT THE PRODUCTS, DESCRIPTIONS, DESIGNS, DATA OR INFORMATION MAY BE USED WITHOUT INFRINGING THE INTELLECTUAL PROPERTY RIGHTS OF OTHERS.** In no case shall the descriptions, information, data or designs provided be considered a part of BASF's terms and conditions of sale. Further, the descriptions, designs, data, and information furnished by BASF hereunder are given gratis and BASF assumes no obligation or liability for the descriptions, designs, data or information given or results obtained all such being given and accepted at the reader's risk.

Basonat, Efka, and Joncryl are registered trademarks of BASF Group.

© BASF Corporation, 2017



BASF Corporation is fully committed to the Responsible Care® initiative in the USA, Canada, and Mexico.
For more information on Responsible Care® go to:
U.S.: www.basf.us/responsiblecare_usa
Canada: www.basf.us/responsiblecare_canada
México: www.basf.us/responsiblecare_mexico

U.S & Canada

BASF Corporation
24710 W Eleven Mile Road
Southfield, MI 48034
ph: 1(800) 231-7868
fax: 1(800) 392-7429
Email: DispersionsPigmentsCC@basf.com
Email: edtech-info@basf.com
www.basf.us/dpsolutions

Mexico

BASF Mexicana, S.A. de C.V.
Av. Insurgentes Sur # 975
Col. Ciudad de los Deportes
C.P. 03710
Mexico, D.F.
Phone: (52-55) 5325-2756
Fax: (52-55) 5723-3011